

**ACI 408.2R-12**

**Report on Bond of  
Steel Reinforcing Bars  
Under Cyclic Loads**

Reported by Joint ACI-ASCE Committee 408



**American Concrete Institute®**



First Printing  
September 2012

**American Concrete Institute®**  
*Advancing concrete knowledge*

## **Report on Bond of Steel Reinforcing Bars Under Cyclic Loads**

Copyright by the American Concrete Institute, Farmington Hills, MI. All rights reserved. This material may not be reproduced or copied, in whole or part, in any printed, mechanical, electronic, film, or other distribution and storage media, without the written consent of ACI.

The technical committees responsible for ACI committee reports and standards strive to avoid ambiguities, omissions, and errors in these documents. In spite of these efforts, the users of ACI documents occasionally find information or requirements that may be subject to more than one interpretation or may be incomplete or incorrect. Users who have suggestions for the improvement of ACI documents are requested to contact ACI via the errata website at [www.concrete.org/committees/errata.asp](http://www.concrete.org/committees/errata.asp). Proper use of this document includes periodically checking for errata for the most up-to-date revisions.

ACI committee documents are intended for the use of individuals who are competent to evaluate the significance and limitations of its content and recommendations and who will accept responsibility for the application of the material it contains. Individuals who use this publication in any way assume all risk and accept total responsibility for the application and use of this information.

All information in this publication is provided "as is" without warranty of any kind, either express or implied, including but not limited to, the implied warranties of merchantability, fitness for a particular purpose or non-infringement.

ACI and its members disclaim liability for damages of any kind, including any special, indirect, incidental, or consequential damages, including without limitation, lost revenues or lost profits, which may result from the use of this publication.

It is the responsibility of the user of this document to establish health and safety practices appropriate to the specific circumstances involved with its use. ACI does not make any representations with regard to health and safety issues and the use of this document. The user must determine the applicability of all regulatory limitations before applying the document and must comply with all applicable laws and regulations, including but not limited to, United States Occupational Safety and Health Administration (OSHA) health and safety standards.

Participation by governmental representatives in the work of the American Concrete Institute and in the development of Institute standards does not constitute governmental endorsement of ACI or the standards that it develops.

Order information: ACI documents are available in print, by download, on CD-ROM, through electronic subscription, or reprint and may be obtained by contacting ACI.

Most ACI standards and committee reports are gathered together in the annually revised ACI Manual of Concrete Practice (MCP).

**American Concrete Institute**  
38800 Country Club Drive  
Farmington Hills, MI 48331  
U.S.A.  
**Phone: 248-848-3700**  
**Fax: 248-848-3701**

[www.concrete.org](http://www.concrete.org)

ISBN 13: 978-0-87031-779-8  
ISBN: 0-87031-779-2

# Report on Bond of Steel Reinforcing Bars Under Cyclic Loads

Reported by Joint ACI-ASCE Committee 408

Adolfo B. Matamoros  
Chair

Michael Keith Thompson  
Secretary

Theresa M. Ahlborn  
Robert W. Barnes\*  
Jean-Jacques Braun  
JoAnn P. Browning†  
James L. Caldwell  
Douglas B. Cleary\*  
Louis J. Colarusso  
James V. Cox  
Christian Dahl  
David Darwin  
Richard A. Devries

Rolf Eligehausen  
Alvin C. Ericson  
Anthony L. Felder  
Scott K. Graham  
Bilal S. Hamad  
Neil M. Hawkins  
Steven E. Holdsworth  
James M. LaFave  
Roberto T. Leon  
LeRoy A. Lutz  
Stavroula J. Pantazopoulou

Max L. Porter  
Julio A. Ramirez  
John F. Silva  
Robert G. Smith  
Ahmet Koray Tureyen\*  
William H. Zehrt Jr.  
Jun Zuo

*Consulting members*  
Gyorgy L. Balazs  
William C. Gallenz  
Brian C. Gerber  
Allen J. Hulshizer  
Kenneth A. Luttrell  
Denis Mitchell  
Mikael P. J. Olsen  
Conrad Paulson  
Melvyn Precious  
Richard A. Ramsey

\*Member, Subcommittee on Repeated Load Effects

†Chair and Editor, Subcommittee on Repeated Load Effects

Note: The contributions of Brett Baker are gratefully acknowledged.

*This report summarizes research on bond strength and behavior of steel reinforcing bars under cyclic loads. The report provides a background to bond problems, discusses the main variables affecting bond performance, and describes bond behavior under cyclic loads. Two general types of cyclic loads are addressed: high-cycle (fatigue) and low-cycle (earthquake and similar). The anchorage behaviors of straight bars, hooked bars, and lap splices are included. Analytical bond models are described, design recommendations are provided for both high- and low-cycle fatigue, and suggestions for further research are given.*

**Keywords:** anchorage; bar slip; bond; bond models; cyclic loads; design recommendations; development length; fatigue; hooks; earthquake loads; splices.

ACI Committee Reports, Guides, and Commentaries are intended for guidance in planning, designing, executing, and inspecting construction. This document is intended for the use of individuals who are competent to evaluate the significance and limitations of its content and recommendations and who will accept responsibility for the application of the material it contains. The American Concrete Institute disclaims any and all responsibility for the stated principles. The Institute shall not be liable for any loss or damage arising therefrom.

Reference to this document shall not be made in contract documents. If items found in this document are desired by the Architect/Engineer to be a part of the contract documents, they shall be restated in mandatory language for incorporation by the Architect/Engineer.

## CONTENTS

### Chapter 1—Introduction and scope, p. 2

- 1.1—Introduction
- 1.2—Scope

### Chapter 2—Notation and definitions, p. 3

- 2.1—Notation
- 2.2—Definitions

### Chapter 3—Bond and anchorage, p. 4

- 3.1—Average bond stresses
- 3.2—Components of bond resistance
- 3.3—Failure modes
- 3.4—Bond mechanisms
- 3.5—Factors affecting bond strength under cyclic loads
- 3.6—Summary

ACI 408.2R-12 supersedes ACI 408.2R-92 and was adopted and published September 2012.

Copyright © 2012, American Concrete Institute.

All rights reserved including rights of reproduction and use in any form or by any means, including the making of copies by any photo process, or by electronic or mechanical device, printed, written, or oral, or recording for sound or visual reproduction or for use in any knowledge or retrieval system or device, unless permission in writing is obtained from the copyright proprietors.

**Chapter 4—Bond behavior under cyclic loads, p. 9**

- 4.1—High-cycle fatigue
- 4.2—Correlation between fatigue and sustained loading
- 4.3—Low-cycle loading
- 4.4—Influence of cracking on bond strength
- 4.5—Debonding to increase shear strength at connections

**Chapter 5—Anchorage under high-cycle fatigue, p. 13**

- 5.1—Straight bar anchorages
- 5.2—Hooked bar anchorages
- 5.3—Lap splices

**Chapter 6—Anchorage under low-cycle loading, p. 17**

- 6.1—Straight bar anchorages
- 6.2—Hooked bar anchorages
- 6.3—Lap splices

**Chapter 7—Analytical bond models, p. 22**

- 7.1—Early models of local bond behavior
- 7.2—Models for local bond-slip effects
- 7.3—Contribution of bond-slip for modeling member and structural system behavior
- 7.4—Bond modeling used in evaluation of existing structures with short lap splices or discontinuous bottom bars through joints
- 7.5—Modeling of high-cycle (fatigue) loading

**Chapter 8—Design and analysis approaches, p. 24**

- 8.1—High-cycle fatigue
- 8.2—Low-cycle loading (earthquake loads)
- 8.3—Recommendations

**Chapter 9—Conclusions and recommendations, p. 29**

- 9.1—Monotonic loading
- 9.2—Cyclic loading
- 9.3—Recommendations for future research

**Chapter 10—References, p. 30****CHAPTER 1—INTRODUCTION AND SCOPE****1.1—Introduction**

The transfer of forces across the interface between concrete and steel by bond stresses is of fundamental importance to many aspects of reinforced concrete behavior. Satisfactory bond performance is an essential goal in detailing reinforcement in structural components. Many detailing provisions in ACI 318 are aimed at preventing bond failures.

Bond stresses in reinforced concrete members arise from two distinct situations. The first is anchorage or development where bars are terminated. The second is flexural bond or the change of force along a bar due to a change in bending moment along the member. Bond performance under static monotonically increasing deformations—referred to as monotonic loading—has been summarized in ACI 352R, ACI 408R, and ACI Committee 408 (1966, 1970, 1979). Bond behavior under cyclic loads received little attention until design for earthquake and live loads became important design topics (ACI Committee 408 1979). Investigations over the past 40 years have clarified some of the important parameters influencing bond behavior under cyclic loads. However, the influence of many of these parameters is understood only qualitatively.

In this report, “bar” means “reinforcing bar” and “ribs” refer to the deformations on deformed reinforcing bars. Longitudinal deformations on reinforcing bars are not classified as ribs. “Bond stress” refers to the stresses along the bar-concrete interface. The steel stresses along the length of the reinforcing bar are modified by transfer of force between the bar and the surrounding concrete along the interface (refer to Fig. 1.1).

The change in bar tensile force  $\Delta F$  between two cracked sections along a flexural member  $\Delta F$  is given by

$$\Delta F = T_1 - T_2 = \left( \frac{M_1}{jd_1} \right) - \left( \frac{M_2}{jd_2} \right) \quad (1.1a)$$

The average bond stress  $u_b$  is usually expressed as

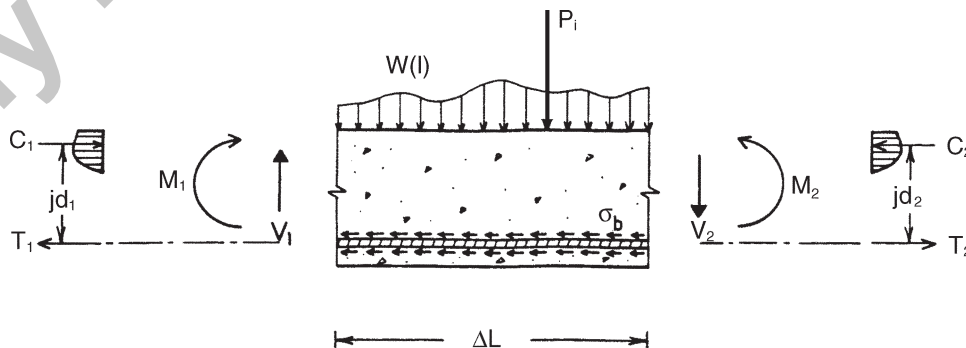


Fig. 1.1—Definition of bond stress.

$$u_b = \frac{q}{\Sigma_o} = \frac{\Delta F}{\Delta L \Sigma_o} = \frac{\Delta f_s (\pi d_b^2 / 4)}{\Delta L (\pi d_b)} = \frac{d_b \Delta f_s}{4 \Delta L} \quad (1.1b)$$

Cyclic loadings are divided into two general categories. The first is designated low-cycle or low-cycle, high-stress loading, or a load history containing less than 100 cycles and having bond stress ranges ( $u_r$ ) greater than 600 psi (4 MPa). Low-cycle loadings commonly result from earthquake and high-wind loadings. The second category is designated high-cycle or fatigue loading with a load history containing thousands or millions of cycles, but at a low bond stress range ( $u_r$ ) typically less than 300 psi (2 MPa). Bridge members, offshore structures, and members supporting vibrating machinery are often subjected to high-cycle or fatigue loading. High-cycle loadings can be a problem at service load levels whereas low-cycle loadings can produce problems at the ultimate limit state.

Bond behavior under cyclic loading can further be subdivided according to the type of stress applied. The first is repeated or unidirectional loading, which implies that the bar stress does not reverse from tension to compression during a load cycle, the usual situation for fatigue loading. The second is stress reversal, where the bar is subjected alternatively to tension and compression. Earthquake loading typically causes stress reversals.

## 1.2—Scope

This report reviews bond and anchorage of steel reinforcing bars in normal and lightweight concrete, with emphasis on bond under cyclic loading. Although the amount of information about the bond behavior of epoxy-coated reinforcing bars subjected to cyclic loading is limited, available references on this topic were reviewed and are presented in the document. Bond and anchorage of prestressing steel and headed reinforcing bars are not addressed in this report. This report serves both designers and researchers, and is organized accordingly. Chapters 3 and 4 present background information on the issue of bond under cyclic loading. Chapters 5, 6, and 7 deal with results of research and development of analytical bond models. Chapters 8 and 9 review international design guidelines dealing with bond under cyclic loads and should be of interest to designers. This report also introduces designers to the basic mechanisms involved in bond, the variables that affect those mechanisms, and differences in bond behavior under cyclic and noncyclic loads.

## CHAPTER 2—NOTATION AND DEFINITIONS

### 2.1—Notation

$A_b$  = cross-sectional area of reinforcing bar, in.<sup>2</sup> (mm<sup>2</sup>)  
 $A_c$  = area of concrete cross section, in.<sup>2</sup> (mm<sup>2</sup>)  
 $A_{tr}$  = area of transverse reinforcement, in.<sup>2</sup> (mm<sup>2</sup>)  
 $BI$  = representation of the severity of bond stresses relative to the bond strength  
 $C$  = concrete cover, in. (mm)  
 $c_b$  = smaller of: (a) the distance from center of a bar or wire to nearest concrete surface; and (b) one-half

the center-to-center spacing of bars or wires being developed, in. (mm)  
 $D$  = development length according to AIJ (1990), in. (mm)  
 $DCH$  = ductility class high, based on the maximum behavior factor  
 $DCM$  = ductility class medium, based on the maximum behavior factor  
 $d$  = depth from extreme compression fiber to center of tensile reinforcement, in. (mm)  
 $d_b$  = diameter of bar, or diameter of bar being developed, in. (mm)  
 $d_{bL}$  = nominal diameter of longitudinal bars, in. (mm)  
 $f_b$  = static bond strength as used for offshore structures, psi (MPa)  
 $f_{br}$  = bond strength at 2,000,000 cycles as used for offshore structures, psi (MPa)  
 $f'_c$  = specified concrete compressive strength, psi (MPa)  
 $f_{cd}$  = design concrete compressive strength, psi (MPa)  
 $f_{cr}$  = stress range in concrete, psi (MPa)  
 $f_{ctm}$  = mean value of the tensile strength of concrete, psi (MPa)  
 $f_{min}$  = minimum stress level, ksi (MPa)  
 $f_r$  = stress range due to live loads and impact recommended by AASHTO, ksi (MPa)  
 $f_{ru}$  = static modulus of rupture, psi (MPa)  
 $f_{rs}$  = existing reinforcement strength based on available development length, psi (MPa)  
 $f_{so}$  = yield strength divided by a factor of safety (typically = 1.15), offshore structures, psi (MPa)  
 $f_y$  = yield strength of bar being developed, psi (MPa)  
 $f_{yd}$  = design value of the yield strength of bars, psi (MPa)  
 $f_{yt}$  = yield strength of transverse reinforcement, psi (MPa)  
 $h$  = depth of member, in. (mm)  
 $h_c$  = width of the column parallel to the bars, in. (mm)  
 $h_j$  = joint dimension parallel to the bar, in. (mm)  
 $jd_i$  = internal moment arm at section  $i$ , in. (mm)  
 $K_{tr}$  = transverse reinforcement index  
 $k_D$  = factor reflecting the ductility class equal to 1 for DCH and to 2/3 for DCM  
 $l$  = total length of the member, in. (mm)  
 $l_b$  = provided length of straight development, lap splice, or standard hook, in. (mm)  
 $l_d$  = development length, in. (mm)  
 $l'_d$  = equivalent straight bar anchorage length corresponding to a hooked bar anchorage, in. (mm)  
 $l_{dh}$  = lead embedment length for a hook, in. (mm)  
 $l_e$  = length of embedment of reinforcement, in. (mm)  
 $M_i$  = moment at section  $i$ , lb-in. (N-m)  
 $N$  = number of cycles to failure  
 $N_{ed}$  = design axial force, lbf (N)  
 $q$  = change of bar force per unit length of bar, lb/in. (N/mm)  
 $r/h$  = ratio of base radius to height of rolled transverse rib  
 $S$  = applied stress range, psi (MPa)  
 $S_{bmax}$  = maximum bond strength as used for offshore structures, psi (MPa)  
 $S_{br}$  = stress range as used for offshore structures, psi (MPa)