


ANSI B3.3 1992 (R1999) (Reaffirmed 2008)

AMERICAN NATIONAL STANDARD

*Accredited Standards
Committee B3*

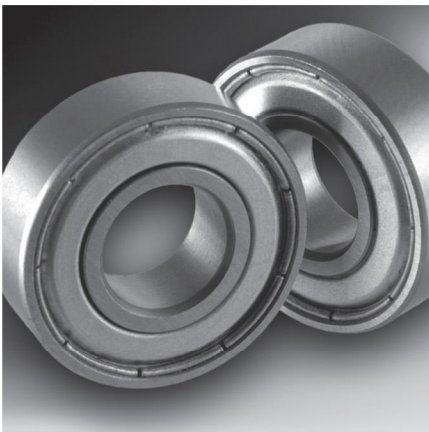

Rolling Element Bearings – Aircraft Engine, Engine Gearbox, and Accessory Applications – Surface Temper Etch

Secretariat

**American Bearing
Manufacturers Association**

Reaffirmed December 17, 2008



ABMA
2025 M Street, NW
Suite 800
Washington, DC 20036
Ph: 202-367-1155
Fax: 202-367-2155

E-mail: info@americanbearings.org
www.americanbearings.org

Currently in preview, click buy full version

American National Standard
for Rolling Element Bearings –
Aircraft Engine, Engine Gearbox,
and Accessory Applications –
Surface Temper Etch

Secretariat

Anti-Friction Bearing Manufacturers Association, Inc.

Approved February 21, 1992

American National Standards Institute, Inc.

American National Standard

Approval of an American National Standard requires verification by ANSI that the requirements for due process, consensus, and other criteria for approval have been met by the standards developer.

Consensus is established when, in the judgment of the ANSI Board of Standards Review, substantial agreement has been reached by directly and materially affected interests. Substantial agreement means much more than a simple majority, but not necessarily unanimity. Consensus requires that all views and objections be considered, and that a concerted effort be made toward their resolution.

The use of American National Standards is completely voluntary; their existence does not in any respect preclude anyone, whether he has approved the standards or not, from manufacturing, marketing, purchasing, or using products, processes, or procedures not conforming to the standards.

The American National Standards Institute does not develop standards and will in no circumstances give an interpretation of any American National Standard. Moreover, no person shall have the right or authority to issue an interpretation of an American National Standard in the name of the American National Standards Institute. Requests for interpretations should be addressed to the secretariat or sponsor whose name appears on the title page of this standard.

CAUTION NOTICE: This American National Standard may be revised or withdrawn at any time. The procedures of the American National Standards Institute require that action be taken periodically to reaffirm, revise, or withdraw this standard. Purchasers of American National Standards may receive current information on all standards by calling or writing the American National Standards Institute.

Published by

**American National Standards Institute
11 West 42nd Street, New York, New York 10036**

Copyright © 1992 by American National Standards Institute
All rights reserved.

No part of this publication may be reproduced in any form, in an electronic retrieval system or otherwise, without prior written permission of the publisher.

Printed in the United States of America

APS2C592/18

Contents

	Page
Foreword	ii
1 Scope	1
2 Normative references	1
3 Definitions	1
4 Requirements	2
5 Test methods	3
6 Acceptance limits	7
7 Records	7

Currently in preview, click buy full versi

Foreword (This foreword is not part of American National Standard B3.3-1992.)

This American National Standard was prepared by a task force consisting of representatives of companies which manufacture rolling element bearings and aircraft, or aircraft engines, or both, in the United States. This standard is issued by the Accredited Standards Committee B3 of the American National Standards Institute as an industrial standard that is intended to be used by aircraft manufacturers, or aircraft engine manufacturers, or both, for the procurement of rolling element bearings for aircraft engine and accessory applications. (This document parallels MIL-STD-867A (USAF), *Military standard temper etch inspection.*)

Suggestions for improvement of this standard will be welcome. They should be sent to the Anti-Friction Bearing Manufacturers Association, Inc., 1101 Connecticut Avenue, NW, Suite 700, Washington, DC 20036.

This standard was processed and approved for submittal to ANSI by the Accredited Standards Committee on Ball and Roller Bearings, B3. Committee approval of this standard does not necessarily imply that all committee members voted for its approval. At the time it approved this standard, the B3 Committee had the following members:

Gene Looft, Chairman
Robert H. Feest, Vice-Chairman
Gary T. Satterfield, Secretary

<i>Organization Represented</i>	<i>Name of Representative</i>
Anti-Friction Bearing Manufacturers Association, Inc.	Robert H. Feest Cameron Gardella P.S. Given C.A. Griffiths W.G. Looft P.S. Orvos B. Pratt S.J. Puckett
Defense Industrial Supply	Leon Silverman
Hydraulic Institute.....	R. Barry Erickson Allen P. Wherry (Alt.)
National Machine Tool Builders Association	L.E. Remillard
Society of Tribologists and Lubrication Engineers	E.E. Pfaffenberger
U.S. Department of the Navy	Adelbert J. Durig

Individual Members
W.J. Anderson
G.W. Argadine
Arthur L. Butterworth
J.C. Clark
W.J. Dorn
Joseph W. Lonski, Jr.
Quoc Nguyen
William E. Poole
John E. Sague
S. Zaritsky

American National Standard for Rolling Element Bearings – Aircraft Engine, Engine Gearbox, and Accessory Applications – Surface Temper Etch

1 Scope

During the manufacture of bearing components, there are many grinding processes which must be carefully controlled. These grinding processes can cause excessive localized heating of the metal being worked and result in altering the metallurgical structure of the alloy. An inspection method of etching the ground surface of these alloys with acids permits detection of those altered structures. This specification for temper etch inspection details the methods and controls for performing etching of ground surfaces for the detection, qualification, and control of altered metallurgical structures of various metallic alloys subjected to grinding.

This specification presents two basic methods of etch, one of alcohol base and another of water base, in addition to use of a photographic gray scale to control bath immersion times and part etching levels. This standard parallels MIL-STD-867A (USAF), *Military standard temper etch inspection*.¹⁾

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this American National Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this American National Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below.

ANSI/SAE ARP 1923, *Qualification and certification of etch inspectors*

MIL-STD 867A-1979, *Military standard temper etch inspection*¹⁾

3 Definitions

3.1 critical surface: Bearing critical surfaces are the surfaces of balls, rollers, and raceways.

3.2 tempering: Areas darker in color than the surrounding etched surfaces indicate lower surface hardness. The areas affected are recognized as dark gray to black in color. The burnt condition may be produced by abnormal tempering as a result of localized overheating due to abusive grinding.

3.3 rehardening: Areas white or very much lighter in color than the surrounding etched surfaces indicate higher surface hardness. The areas affected may be recognized as white islands surrounded by a border of tempered metal (black). The rehardened condition is produced by localized overheating that exceeds the critical temperature of the metal. The rehardening condition is the result of very severe abusive grinding.

3.4 decarburization: Areas lighter in color than the surrounding unburnt areas indicate a lower surface hardness. This discrepancy is unrelated to abusive grinding. These areas are deficient in carbon (*decarburization*) and are produced by certain heat treatment conditions.

3.5 false indications: Indications caused by smears, stains, certain wheel patterns, buffing wheel patterns, smutty finishes, fingerprints,

¹⁾ Available from the Naval Publications and Forms Center, Attention NPFC-3064, 5801 Tabor Avenue, Philadelphia, PA 19120.