


Australian Standard[®] 1279—1985

COPPER REFINERY SHAPES

AS/NZS 1279:1996
Copper refinery shapes 8pp D
Specifies requirements for grades of copper supplied as refined shapes in the form of billets, cakes (vertically or continuously cast) and cathodes. Appendices provide information on related designations and the relationship between resistivity and conductivity.
(MT/2): Supersedes AS 1279—1985;
DR 94390: Publication date 1996-04-05.

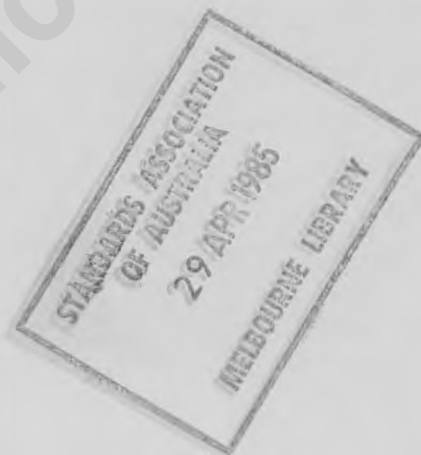

STANDARDS ASSOCIATION OF AUSTRALIA
Incorporated by Royal Charter

This Australian standard was prepared by Committee MT/2, Copper and Copper Alloys. It was approved on behalf of the Council of the Standards Association of Australia on 15 January 1985 and published on 4 April 1985.

The following interests are represented on Committee MT/2:

Australian Foundry Institute
Australian Welding Institute
Confederation of Australian Industry
Copper Development Association of Australia Limited
Coppermetals Extruders Council of Australia
Department of Defence
Metropolitan Water, Sewerage and Drainage Board, N.S.W.
Telecom Australia
Universities

Review of Australian Standards. To keep abreast of progress in industry, Australian standards are subject to periodic review and are kept up-to-date by the issue of amendments or new editions as necessary. It is important therefore that standards users ensure that they are in possession of the latest edition, and any amendments thereto.

For details of all SAA publications will be found in the Catalogue of Australian Standards; this information is supplemented each month by SAA's journal 'The Australian Standard', which subscribing members receive, and which gives details of new publications, new editions and amendments, and of withdrawn standards.

Suggestions for improvements to Australian standards, addressed to the head office of the Association, are welcomed. Notification of any inaccuracy or ambiguity found in an Australian standard should be made without delay in order that the matter may be investigated and appropriate action taken.

AUSTRALIAN STANDARD

COPPER REFINERY SHAPES

AS 1279—1985

First published (as AS H55 to H57).....	1951
Revised	1961
First published as AS 1279.....	1974
Second edition.....	1980
Third edition.....	1985

**PUBLISHED BY THE STANDARDS ASSOCIATION OF AUSTRALIA
STANDARDS HOUSE, 80 ARTHUR ST, NORTH SYDNEY, N.S.W.**

ISBN 0 7262 3663 2

PREFACE

This edition of this standard was prepared under the direction of the Association's Committee on Copper and Copper Alloys by its subcommittee on refined copper, to supersede AS 1279-1980. It specifies requirements for refined copper supplied as refinery shapes in the form of cathodes, vertically and continuously cast cakes and billets, and wire bars.

In this edition, the two phosphorus deoxidized copper grades have had their minimum phosphorus content increased slightly to comply with the equivalent wrought grades and those specified by the American Society for Testing and Materials (ASTM).

In this standard, the various grades of copper listed in Table 1.1 are identified in the same manner as that adopted by Technical Committee No 26, Copper and Copper Alloys, of the International Organization for Standardization, and the British Standards Institution in BS 6017, Copper Refinery Shapes. It is also similar to that adopted by ASTM.

CONTENTS

	<i>Page</i>
SECTION 1. SCOPE AND GENERAL	
1.1 Scope	3
1.2 Referenced Documents.....	3
1.3 Designation.....	3
1.4 Definitions	3
1.5 Quality Requirements	4
1.6 Manufacturing Tolerances	4
1.7 Physical Condition	4
1.8 Marking	4
1.9 Lots	4
1.10 Claims	4
SECTION 2. MANUFACTURING TOLERANCES FOR CAKES, BILLETS AND WIRE BARS	
2.1 Scope of Section	5
2.2 Cakes	5
2.3 Billets	5
2.4 Wire Bars	5
APPENDICES	
A Purchasing Guidelines	7
B Related Composition Specifications	9
C Notes on Resistivity and Conductivity Relationships	10
D Claim Procedures	12

©Copyright — STANDARDS ASSOCIATION OF AUSTRALIA 1985

Users of standards are reminded that copyright subsists in all SAA publications. No part of this publication may be reproduced, stored in a retrieval system in any form or transmitted by any means without prior permission in writing of the Standards Association of Australia.

STANDARDS ASSOCIATION OF AUSTRALIA

Australian Standard
for
COPPER REFINERY SHAPES

SECTION 1. SCOPE AND GENERAL

1.1 SCOPE. This standard specifies requirements for grades of copper supplied in the form of refinery shapes, as follows:

- (a) Cathodes.
- (b) Cakes (vertically or continuously cast).
- (c) Billets (vertically or continuously cast).
- (d) Wire bars (horizontally cast).

NOTES:

1. Copper with special qualities, e.g. specific oxygen limits, may be supplied by agreement (see Paragraph A3 of Appendix A).
2. Guidelines to purchasers on requirements that must be specified by the purchaser and those that must be agreed at the time of enquiry and/or order are given in Appendix A.

1.2 REFERENCED DOCUMENTS. The following documents are referred to in this standard:

AS 1515	Methods for the Analysis of Copper Alloys Part 3—Silver in Copper Alloys (Atomic Absorption Spectrometric Method)
AS 1696	Methods for the Analysis of Copper Part 1—Phosphorus in Copper (Spectrophotometric Method)
AS 2738	Copper and Copper Alloys—Compositions and Designations Part 1—Refinery Products
AS K208	Methods for the Analysis of Unalloyed Copper Part 1—Method for the Electrolytic Determination of Copper in Unalloyed Copper Containing not less than 99.85 Percent Copper

ISO 2626	Copper—Hydrogen Embrittlement Test
ISO/R1811	Chemical Analysis of Copper and Copper Alloys—Sampling of Copper Refinery Shapes
ASTM B193	Tests for Resistivity of Electrical Conductor Material

1.3 DESIGNATION. The designation of the coppers, as given in Table 1.1 and Appendix B, shall be in accordance with AS 2738.1.

1.4 DEFINITIONS. For the purpose of this standard, the following definitions apply:

1.4.1 Terms relating to refinery shapes.

1.4.1.1 Refinery shapes—a general term for unwrought products obtained by refining or by refining and casting processes; for example, cathode, cake, billet and wire bar.

1.4.1.2 Cathode—a rough flat refinery shape made by electrolytic deposition and normally used for remelting.

1.4.1.3 Cake—a cast refinery shape of rectangular cross-section, generally used for rolling into plate, sheet, strip or profiles.

1.4.1.4 Billet—a cast refinery shape of circular cross-section, used for the production of tube, rod, bar, profiles or forgings.

1.4.1.5 Wire bar—a cast refinery shape, normally of approximately square cross-section, with tapered ends, principally used for rolling into rod or flat products for subsequent processing into wire, strip or profiles.

TABLE 1.1
CHEMICAL COMPOSITION AND ELECTRICAL PROPERTIES

Designation*	Chemical composition, percent				Electrical resistivity† Ω.g/m ² 20°C	Conductivity %IACS
	Copper (incl. silver)	Phosphorus		Silver		
	min.	min.	max.	min.	max.	min.
Cu-CATH	99.90	—	—	—	0.153 28	100
Cu-ETP	99.90	—	—	—	0.153 28	100
Cu-DLP	99.90	0.004	0.012	—	—	—
Cu-DHP	99.90	0.015	0.040	—	—	—
Cu-Ag	99.90	—	—	‡	0.153. 28	100

* Appendix B gives information on related compositions.

† Appendix C contains notes on resistivity and conductivity relationships.

‡ By agreement (see Paragraph A3.2 of Appendix A).