


YIELD STRENGTH VALUES UP TO MAXIMUM TEMPERATURE DESIGN

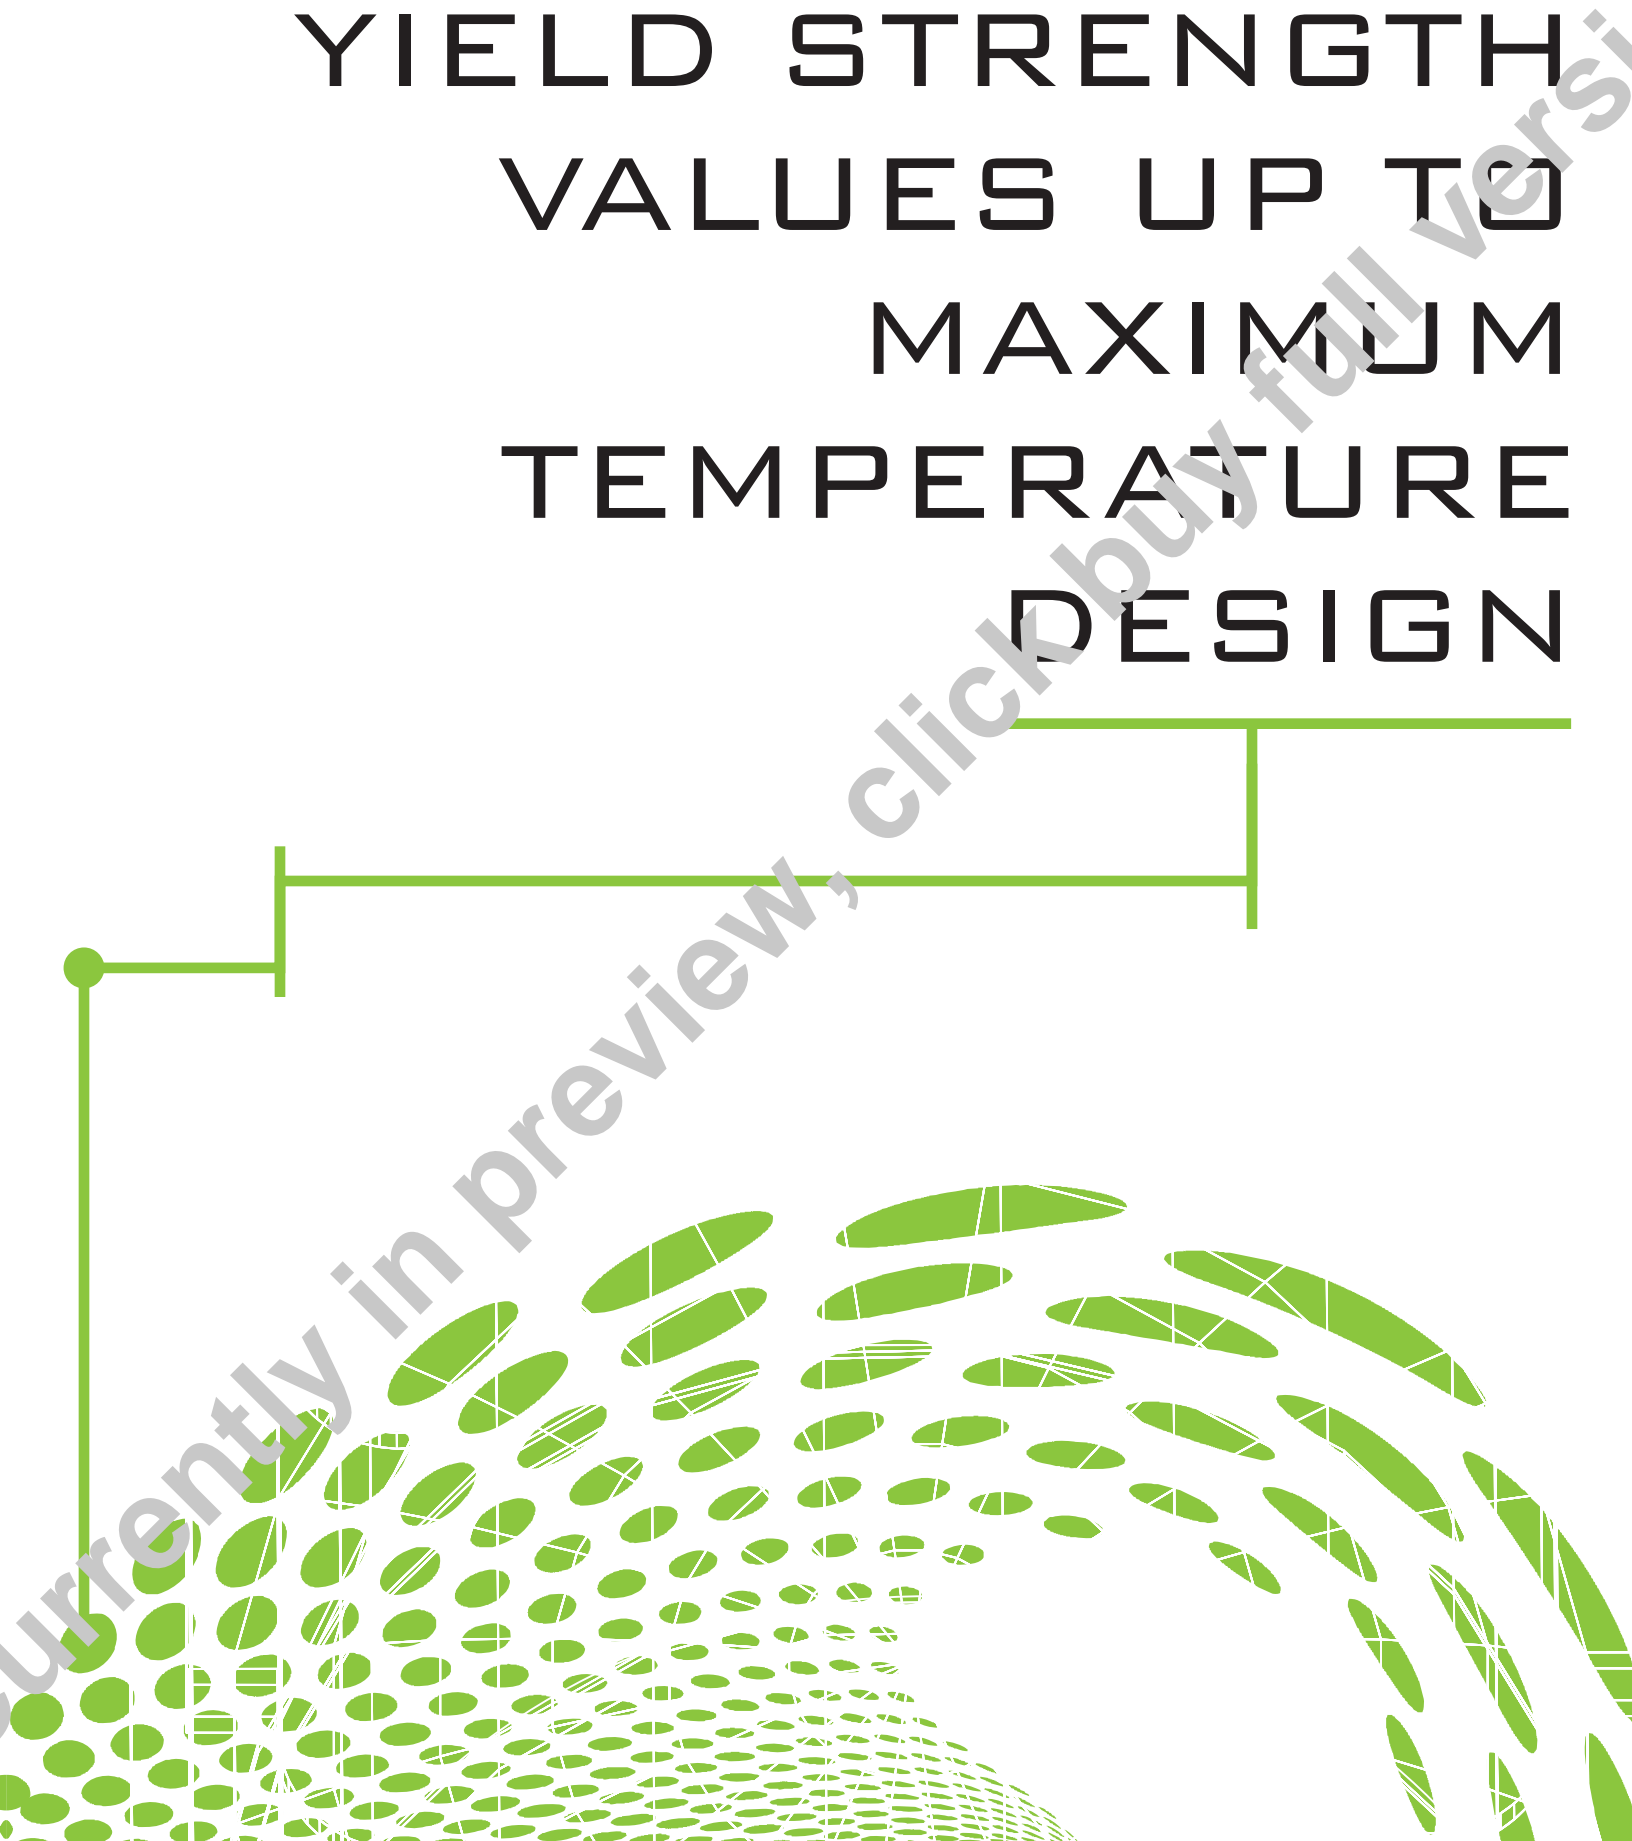

STP-PT-087

YIELD STRENGTH VALUES UP TO MAXIMUM TEMPERATURE DESIGN

Prepared by:

Wolfgang Hoffelner
RWH-consult GmbH

ASME STANDARDS
TECHNOLOGY, LLC

Date of Issuance: June 22, 2018

This publication was prepared by ASME Standards Technology, LLC (“ASME ST-LLC”) and sponsored by The American Society of Mechanical Engineers (“ASME”).

Neither ASME, ASME ST-LLC, the author, nor others involved in the preparation or review of this publication, nor any of their respective employees, members, or persons acting on their behalf, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe upon privately owned rights.

Reference herein to any specific commercial product, process, or service by trade name, trade mark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by ASME ST-LLC or others involved in the preparation or review of this publication, or any agency thereof. The views and opinions of the authors, contributors and reviewers of the publication expressed herein do not necessarily reflect those of ASME ST-LLC or others involved in the preparation or review of this publication, or any agency thereof.

ASME ST-LLC does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a publication against liability for infringement of any applicable Letters Patent, nor assumes any such liability. Users of a publication are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this publication.

ASME is the registered trademark of the American Society of Mechanical Engineers.

No part of this document may be reproduced in any form,
in an electronic retrieval system or otherwise,
without the prior written permission of the publisher.

ASME Standards Technology, LLC
Two Park Avenue, New York, NY 10016-5990

ISBN No. 978-0-7918-7242-0
Copyright © 2018
ASME Standards Technology, LLC
All Rights Reserved

TABLE OF CONTENTS

Foreword.....	viii
Abstract.....	ix
Abbreviations and Acronyms	x
1 INTRODUCTION.....	1
2 STEELS.....	5
2.1 S20910 / XM-19/ 22Cr-13Ni-5Mn up to 1200°F	5
2.2 S30400/ 304/ 18Cr-8Ni up to 1500°F.....	8
2.3 S30403/ 304L/18Cr-8Ni up to 1200°F	11
2.4 S30908/ 309 S/ 23Cr-12Ni up to 1500°F.....	14
2.5 S31008/ 310 S/ 25Cr-20Ni up to 1500°F.....	17
2.6 S31600/SS 316/ 16Cr-12Ni-2Mo up to 1500°F.....	20
2.7 S31603/ 316L/ 16Cr-12Ni-2Mo up to 1200°F.....	22
2.8 S31635/ 316Ti/16Cr-12Ni-2Mo-Ti up to 1500°F.....	24
2.9 S31700/ SS317/and S31703/SS317 L/ 18Cr-13Ni-3Mo up to 1500°F (1200°F).....	27
2.10 S32100/ SS321/ 18Cr-10Ni-Ti up to 1500°F.....	28
2.11 S34700/ SS347 and S34800/ SS348/ 18Cr-10Ni-Cb up to 1500°F	31
3 COPPER.....	34
3.1 C23000 / Cu 230 / 85 Cu-15 Zn up to 500°F.....	34
3.2 C28000 / Cu 280 / 59 Cu-40Zn-0.07Fe-0.3Pb up to 500°F.....	35
3.3 C36500 / Cu 365 / 60Cu-39.4 Zn-0.6 Pb.....	37
3.4 C44300 / Cu 443 C44400 / Cu 444 C44500 / Cu 445 up to 500°F	38
3.5 C46400 / Cu 464 C46500 / Cu-465 up to 500°F.....	41
3.6 C64200 / Cu 642 / 91.2 Cu, 7.0 Al, 1.8 Ni up to 500°F.....	42
3.7 C68700 / Cu 687 / 77.5 Cu, 20.5 Zn, 2.0 Al, 0.1 As up to 500°F.....	44
3.8 C70400 / Cu 704 / 92.4 Cu, 5.5 Ni, 1.0 Fe, 0.6 Mn up to 500°F.....	46
3.9 C71000 / Cu 710 / 79 Cu, 21 Ni up to 700°F	47
4 NICKEL	49
4.1 N02201 / Ni 201 up to 1200°F.....	49
4.2 N06002 / Ni X up to 1650°F.....	52
4.3 N06022 up to 1500°F.....	55
4.4 N06600 / Ni 600 up to 1200°F.....	58
4.5 Annealed.....	58
4.6 Hot Worked.....	61
4.7 Seamless Pipe	63
4.8 N06625 / Ni 625 SA up to 1600°F.....	65
4.9 N06625 / Ni 625 Ann up to 1200°F.....	68
4.10 N08330 / Ni 330 up to 1650°F.....	71
4.11 N08800 / Ni 800 up to 1500°F	74
4.12 N08810 / Ni 800H and N08811 / Ni 811 up to 1650°F	77
4.13 N10276 / Ni C276 up to 1500°F	80

4.14 N10003 / Ni N / Hastelloy N up to 1500°F.....83
 Appendix A.....86

LIST OF FIGURES

Figure 1-1: List of steels and required maximum temperatures2
 Figure 1-2: Current ASME Y-1 data and data from the current new evaluation3
 Figure 1-3: Matching current Y-1 data and new evaluation by shifting the new curve. Using 1.045 instead of 1.07 as constant in the polynomial for the new values3
 Figure 1-4: Matching current Y-1 data and new evaluation by making a joint polynomial fit.....4
 Figure 2-1: YS stress ratios from current ASME (2015) Y-1 Tables compared with literature data (Material: S20910 / XM-19/ 22Cr-13Ni-5Mn)5
 Figure 2-2: Graphical representations of the customary Y-1 data S20910 / XM-19/ 22Cr-13Ni-5Mn5
 Figure 2-3: Graphical representations of the metric Y-1 data S20910 / XM-19/ 22Cr-13Ni-5Mn6
 Figure 2-4: YS stress ratios (customary and metric) for XM-19 up to 1200 F7
 Figure 2-5: YS stress ratios from current ASME (2015) Y-1 Tables compared with literature data (Material: S30400/ 304/ 18Cr-8Ni).....8
 Figure 2-6: YS stress ratios from current ASME (2015) Y-1 Tables compared with polynomial fit through literature data8
 Figure 2-7: Plot of proposed customary YS stress reduction factors for S30400. Y-1-new obtained using 1.07 instead of 1.1 in the polynomial9
 Figure 2-8: Plot of proposed metric YS stress reduction factors for S30400. Y-1-new obtained using 1.07 instead of 1.1 in the polynomial9
 Figure 2-9: YS stress ratios (customary and metric) for SS304 up to 1500 F. Y-1-new obtained using 1.07 instead of 1.1 in the polynomial10
 Figure 2-10: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S30403)11
 Figure 2-11: Polynomial fit through relevant data (material: S30403)11
 Figure 2-12: Plot of proposed customary YS stress reduction factors for S304L. Y-1-new obtained using 1.07 instead of 1.1 in the polynomial12
 Figure 2-13: Plot of proposed metric YS stress reduction factors for S304L. Y-1-new obtained using 1.16 instead of 1.1 in the polynomial12
 Figure 2-14: YS stress ratios (customary and metric) for S304L up to 1200°F. Y-1-new obtained using 1.16 instead of 1.1 in the polynomial13
 Figure 2-15: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S30908)14
 Figure 2-16: Polynomial fit through relevant data (material S30908)14
 Figure 2-17: Plot of proposed customary YS stress reduction factors for S3090815
 Figure 2-18: Plot of proposed metric YS stress reduction factors for S3090815
 Figure 2-19: YS stress ratios (customary and metric) for S30908 up to 1500°F16
 Figure 2-20: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S31008)17
 Figure 2-21: Polynomial fit through relevant data (material: S31008)17
 Figure 2-22: Plot of proposed customary YS stress reduction factors for S3100818
 Figure 2-23: Plot of proposed metric YS stress reduction factors for S3100818
 Figure 2-24: YS stress ratios (customary and metric) for S31008 up to 1500°F19
 Figure 2-25: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S31600)20
 Figure 2-26: Plot of proposed customary YS stress reduction factors for S3160020
 Figure 2-27: Plot of proposed metric YS stress reduction factors for S3160021
 Figure 2-28: YS stress ratios (customary and metric) for S31600 up to 1500°F21

Figure 2-29: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S31603)22

Figure 2-30: Plot of proposed customary YS stress reduction factors for S3160322

Figure 2-31: Plot of proposed metric YS stress reduction factors for S3160323

Figure 2-32: Yield strength reduction factors for S31603 up to 1200°F23

Figure 2-33: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S31635)24

Figure 2-34: ATI data for S316, 316L, 317, 317L and 316Ti24

Figure 2-35: Plot of proposed customary YS stress reduction factors for S3163525

Figure 2-36: Plot of proposed metric YS stress reduction factors for S3163525

Figure 2-37: Yield strength reduction factors for S31635 up to 1500°F25

Figure 2-38: YS strength reduction factors for 317 and 317L from current Y-1 Tables27

Figure 2-39: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S32100)28

Figure 2-40: Plot of proposed customary YS stress reduction factors for S32100. Y-1-new obtained using 1.04 instead of 1.06 in the polynomial28

Figure 2-41: Plot of proposed metric YS stress reduction factors for S32100. Y-1-new obtained using 1.04 instead of 1.06 in the polynomial29

Figure 2-42: YS stress ratios (customary and metric) for S32100 up to 1500°F. Y-1-new obtained using 1.04 instead of 1.06 in the polynomial30

Figure 2-43: YS strength reduction factors from current ASME (2015)-Y-1 Tables compared with literature data (material: S34700)31

Figure 2-44: Plot of proposed customary YS stress reduction factors for S34700. Y-1-new obtained using 1.08 instead of 1.1 in the polynomial31

Figure 2-45: Plot of proposed metric YS stress reduction factors for S34700. Y-1-new obtained using 1.08 instead of 1.1 in the polynomial32

Figure 2-46: Yield strength reduction factors for SS347 and S348 up to 1500°F33

Figure 3-1: Comparison of available data for C2300034

Figure 3-2: Proposed YS stress ratios for C23000 up to 600°F. Current B1 Table values remain the same34

Figure 3-3: Yield strength reduction factor for C2300035

Figure 3-4: Comparison of available data; B-1: (Table 1B allowable stress*3)/(2 YS at RT) (material C28000)35

Figure 3-5: Proposed YS stress ratios for C28000 up to 500°F. Current B-1 Table values remain the same36

Figure 3-6: Yield strength reduction factors for C2800036

Figure 3-7: Comparison of available data37

Figure 3-8: Proposed YS stress ratios for C36500 up to 500°F37

Figure 3-9: Yield strength reduction factors for C3650038

Figure 3-10: Comparison of available data; C44300, C44400 and C44500 are expected to show the same tensile data. B-1: (Table 1B allowable stress*3)/(2 YS at RT)38

Figure 3-11: Proposed YS stress ratios for C44300, C44400 and C4450039

Figure 3-12: Proposed YS stress ratios for annealed C44300, C44400 and C4450039

Figure 3-13: Comparison of data from Record 15-539 with data shown in Figure 3-10. It is proposed to use the 15-539 data40

Figure 3-14: Yield strength reduction factors for C44300, C44400 and C44500 based on 15-539 data40

Figure 3-15: Comparison of available data; C46400 and C46500 are expected to show the same tensile data. B-1: (Table 1B allowable stress*3)/(2 YS at RT)41

Figure 3-16: Proposed YS stress ratios for C46400 and C4650041

Figure 3-17: Yield strength reduction factors for C46400 and C4650042

Figure 3-18: Comparison of available data; C64200. 1-B: (Table 1B allowable stress*3)/(2 YS at RT)42

Figure 3-19: Proposed YS stress ratios for C64200.....43

Figure 3-20: Yield strength reduction factors for C64200.....43

Figure 3-21: Comparison of available data for C68700. Y-1: (Table 1B allowable stress*3)/(2 YS at RT).....44

Figure 3-22: Proposed YS stress ratios for C68700.....44

Figure 3-23: Comparison of data for C68700 from Gene Shapiro with the current evaluation. Up to 700°F no differences were found.....45

Figure 3-24: Yield strength reduction factors for C68700.....45

Figure 3-25: Comparison of available data for C70400.....46

Figure 3-26: Proposed YS stress ratios for C70400.....46

Figure 3-27: Yield strength reduction factors for C70400.....47

Figure 3-28: Comparison of available data for C71000. 1-B: (Table 1B allowable stress*3)/(2 YS at RT).....47

Figure 3-29: Proposed YS stress ratios for C71000.....48

Figure 3-30: Yield strength reduction factors for C71000.....48

Figure 4-1: Comparison of available data for N02201. Y-1: Taken from Table IID Y-1.....49

Figure 4-2: Proposed YS stress ratios for N02201.....49

Figure 4-3: Plot of proposed customary YS stress reduction factors for N02201 using 1.03 instead of 1.07 in the polynomial50

Figure 4-4: Plot of proposed metric YS stress reduction factors for N02201 using 1.03 instead of 1.07 in the polynomial50

Figure 4-5: Yield strength reduction factors for N02201 using 1.03 instead of 1.07 in the polynomial.....51

Figure 4-6: Comparison of available data for N06002. Y-1 Hast Y. Table IID Y-1 values.....52

Figure 4-7: Proposed YS stress ratios for N06002.....52

Figure 4-8: Plot of proposed customary YS stress reduction factors for N0600253

Figure 4-9: Plot of proposed metric YS stress reduction factors for N06002.....53

Figure 4-10: Yield strength reduction factors for N06002.....54

Figure 4-11: Comparison of available data for N06022. Y-1: Taken from Table IID Y-155

Figure 4-12: Proposed YS stress ratios for N0602255

Figure 4-13: Plot of proposed customary YS stress reduction factors for N06022 using 1.09 instead of 1.0834 in the polynomial56

Figure 4-14: Plot of proposed metric YS stress reduction factors for N06022 using 1.09 instead of 1.0834 in the polynomial56

Figure 4-15: Yield strength reduction factors for N06022 using 1.09 instead of 1.0834 in the polynomial57

Figure 4-16: Comparison of available data for N06600. Several Y-1 values were taken from Table IID Y-158

Figure 4-17: Proposed YS stress ratios for N06600 annealed58

Figure 4-18: Plot of proposed customary YS stress reduction factors for N06600 annealed using 1.05 instead of 1.10 in the polynomial.....59

Figure 4-19: Plot of proposed metric YS stress reduction factors for N06600 annealed using 1.05 instead of 1.10 in the polynomial59

Figure 4-20: Yield strength reduction factors for N06600 annealed using 1.05 instead of 1.1 in the polynomial60

Figure 4-21: Proposed YS stress ratios for N06600 hot worked61

Figure 4-22: Plot of proposed customary YS stress reduction factors for N06600 hot worked using 0.98 instead of 1.0078 in the polynomial.....61

Figure 4-23: Plot of proposed metric YS stress reduction factors for N06600 hot worked using 0.98 instead of 1.0078 in the polynomial.....62

Figure 4-24: Yield strength reduction factors for N06600 hot worked using 0.98 instead of 1.0078 in the polynomial62

Figure 4-25: Proposed YS stress ratios for N06600 seamless pipe 63

Figure 4-26: Plot of proposed customary YS stress reduction factors for N06600 seamless pipe using 1.045 instead of 1.07 in the polynomial..... 63

Figure 4-27: Plot of proposed metric YS stress reduction factors for N06600 seamless pipe using 1.045 instead of 1.07 in the polynomial..... 64

Figure 4-28: Yield strength reduction factors for N06600 seamless pipe using 1.045 instead of 1.07 in the polynomial 64

Figure 4-29: Comparison of available data for N06625 (sol annealed). Y-1 sol ann values were taken from Table IID Y-1 65

Figure 4-30: Proposed YS stress ratios for N06625 solution annealed..... 65

Figure 4-31: Plot of proposed customary YS stress reduction factors for N06625 solution annealed using 1.07 instead of 1.04 in the polynomial 66

Figure 4-32: Plot of proposed metric YS stress reduction factors for N06625 solution annealed using 1.07 instead of 1.04 in the polynomial..... 66

Figure 4-33: Yield strength reduction factors for N06625 solution annealed using 1.07 instead of 1.04 in the polynomial 67

Figure 4-34: Comparison of available data for N06625 (annealed). Y-1 ann values were taken from Table IID Y-1 68

Figure 4-35: Proposed YS stress ratios for N06625 annealed 68

Figure 4-36: Plot of proposed customary YS stress reduction factors for N06625 annealed 69

Figure 4-37: Plot of proposed metric YS stress reduction factors for N06625 annealed..... 69

Figure 4-38: Yield strength reduction factors for N06625 annealed 70

Figure 4-39: Comparison of available data for N08330. Y-1 values were taken from Table IID-Y1 .. 71

Figure 4-40: Proposed YS stress ratios for N08330 71

Figure 4-41: Plot of proposed customary YS stress reduction factors for N08330 using 1.045 instead of 1.07 in the polynomial 72

Figure 4-42: Plot of proposed metric YS stress reduction factors for N08330 using 1.045 instead of 1.07 in the polynomial 72

Figure 4-43: Yield strength reduction factors for N08330 using 1.045 instead of 1.07 in the polynomial 73

Figure 4-44: Comparison of available data for N08800. 800 Y-1 values taken from Table IID Y-1 ... 74

Figure 4-45: Proposed YS stress ratios for N08800 74

Figure 4-46: Plot of proposed customary YS stress reduction factors for N08800 75

Figure 4-47: Plot of proposed metric YS stress reduction factors for N08800..... 75

Figure 4-48: Yield strength reduction factors for N08800..... 76

Figure 4-49: Comparison of available data for N08810 and N08811. Y-1 values were taken from Table IID Y-1 77

Figure 4-50: Proposed YS stress ratios for N08810 and N08811 77

Figure 4-51: Plot of proposed customary YS stress reduction factors for N08810 and N08811 78

Figure 4-52: Plot of proposed metric YS stress reduction factors for N08810 and N08811 78

Figure 4-53: Yield strength reduction factors for N08810 and N08811 79

Figure 4-54: Comparison of available data for N10276. Y-1 values were taken from Table IID Y-1 . 80

Figure 4-55: Proposed YS stress ratios for N10276 80

Figure 4-56: Plot of proposed customary YS stress reduction factors for N10276 81

Figure 4-57: Plot of proposed metric YS stress reduction factors for N10276..... 81

Figure 4-58: Yield strength reduction factors for N10276..... 82

Figure 4-59: Comparison of available data for N10003. Hast N Y-1 values taken from Table IID Y-183

Figure 4-60: Proposed YS stress ratios for N10003 83

Figure 4-61: Plot of proposed customary YS stress reduction factors for N10003 84

Figure 4-62: Plot of proposed metric YS stress reduction factors for N10003..... 84

Figure 4-63: Yield strength reduction factors for N10003..... 85

FOREWORD

Table Y-1 of ASME Boiler & Pressure Vessel Code (BPVC) Section II Part D currently provides yield strength values up to 1000°F maximum, with some yield strength values at lower temperatures. The maximum design temperature in Tables 1A and 1B may be higher, therefore yield strength values need to be provided to be able to expand Table Y-1 up to the maximum temperature design of Table 1A-1B-5A and Table 1A-1B-5B for construction pursuant to ASME BPVC Section VIII Division 1 and Division 2.

The author acknowledges, with deep appreciation, the activities of ASME staff and volunteers who have provided valuable technical input, advice and assistance with review of, commenting on, and editing of, this document.

Established in 1880, the ASME is a professional not-for-profit organization with more than 135,000 members and volunteers promoting the art, science and practice of mechanical and multidisciplinary engineering and allied sciences. ASME develops codes and standards that enhance public safety, and provides lifelong learning and technical exchange opportunities benefiting the engineering and technology community. Visit <https://www.asme.org/> for more information.

ASME ST-LLC is a not-for-profit Limited Liability Company, with ASME as the sole member, formed in 2004 to carry out work related to new and developing technology. ASME ST-LLC's mission includes meeting the needs of industry and government by providing new standards-related products and services, which advance the application of emerging and newly commercialized science and technology, and providing the research and technology development needed to establish and maintain the technical relevance of codes and standards. Visit <http://asmestllc.org/> for more information.

ABSTRACT

The publication provides yield strength data for different materials (steels, copper, and nickel-base) for temperatures greater than the ones provided in current ASME BPVC IID/Y-1 tables. For this purpose, data from different sources were obtained. The current Y-1 Tables values were not to be affected; therefore, the data had to be fit to those values (customary and metric). This led to bumps in the curves, which were normalized by shifting the data of the current report (in the percent range). Providing smooth curves via a polynomial fit through all data is certainly an alternative, however, this would also affect values in ASME BPVC IID/Y-1 tables. The data provided in this report would allow for such a treatment.

ABBREVIATIONS AND ACRONYMS

AISI	American Iron and Steel Institute
ASM	American Society for Metals
ASME	American Society of Mechanical Engineers
ASTM	American Society for Testing and Materials
ATI	Allegheny Technologies
BPVC	ASME Boiler & Pressure Vessel Code
DOE	United States Department of Energy
EURO INOX	European Stainless Steel Development Association
JTEVA	Journal of Testing and Evaluation
NIDI	Nickel Development Institute
ORNL	Oak Ridge National Laboratory
VDM	Vereinigte Deutsche Metallwerke AG

1 INTRODUCTION

In ASME BPVC Section VIII Division 1, the yield strength (S_y) is used directly, or indirectly through the allowable primary and secondary stress limit ($SPS = \max [3S, 2S_y]$), and in many of the design rules, such as:

- (a) UG-28 and UG-33 – External pressure: Calculation of allowable external pressure on cylinders and heads – S_y [see UG-28(c)(2) Step 3]
- (b) Part UHX – Shell-and-tube heat exchangers: Secondary stress limit in tube sheets, channels, shells, and expansion joints – SPS 27 October 2015 Page 2 of 6
- (c) Part UHX – Fixed tube sheet heat exchangers: Allowable tube buckling stress at design temperature – S_y
- (d) Appendix 1-4 – Design of Head: Yield strength at design temperature – S_y
- (e) Appendix 1-5 and 1-8 – Conical Reducers: Discontinuity stress limit and operating metal temperature – SPS
- (f) Appendix 5 – Flanged-and-Flued and Flanged-Only Expansion Joints: Thermally induced stress limit at operating metal temperature – SPS
- (g) Appendix 13 – Noncircular Vessels: Plate buckling stress at design temperature
- (h) Appendix 26 – Bellows Expansion Joints: Calculation of instability due to internal pressure at design temperature – S_y
- (i) Non-mandatory Appendix A – Tube-to-Tube sheet Joint Loads: Calculation of tube joint interface pressure at the operating metal temperature – S_y

Because Table Y-1 provides yield strength values up to 1000°F maximum, yield strength values up to the maximum temperature design are needed.

Due to the large number of missing values, the materials investigated will be restricted to the list below, which correspond to the most commonly used materials for heat exchangers.