



**American Water Works
Association**

Dedicated to the World's Most Important Resource®

ANSI/AWWA C300-16
(Revision of ANSI/AWWA C300-11)

AWWA Standard

Reinforced Concrete Pressure Pipe, Steel- Cylinder Type

Effective date: Jan. 1, 2017.

First edition approved by AWWA Board of Directors Dec. 11, 1947.

This edition approved June 19, 2016.

Approved by American National Standards Institute Aug. 10, 2016.




AWWA Standard

This document is an American Water Works Association (AWWA) standard. It is not a specification. AWWA standards describe minimum requirements and do not contain all of the engineering and administrative information normally contained in specifications. The AWWA standards usually contain options that must be evaluated by the user of the standard. Until each optional feature is specified by the user, the product or service is not fully defined. AWWA publication of a standard does not constitute endorsement of any product or product type, nor does AWWA test, certify, or approve any product. The use of AWWA standards is entirely voluntary. This standard does not supersede or take precedence over or displace any applicable law, regulation, or code of any governmental authority. AWWA standards are intended to represent a consensus of the water industry that the product described will provide satisfactory service. When AWWA revises or withdraws this standard, an official notice of action will be placed on the first page of the Official Notice section of *Journal – American Water Works Association*. The action becomes effective on the first day of the month following the month of *Journal – American Water Works Association* publication of the official notice.

American National Standard

An American National Standard implies a consensus of those substantially concerned with its scope and provisions. An American National Standard is intended as a guide to aid the manufacturer, the consumer, and the general public. The existence of an American National Standard does not in any respect preclude anyone, whether that person has approved the standard or not, from manufacturing, marketing, purchasing, or using products, processes, or procedures not conforming to the standard. American National Standards are subject to periodic review, and users are cautioned to obtain the latest editions. Producers of goods made in conformity with an American National Standard are encouraged to state on their own responsibility in advertising and promotional materials or on tags or labels that the goods are produced in conformity with particular American National Standards.

CAUTION NOTICE: The American National Standards Institute (ANSI) approval mark on the front cover of this standard indicates completion of the ANSI approval process. This American National Standard may be revised or withdrawn at any time. ANSI procedures require that action be taken to reaffirm, revise, or withdraw this standard no later than five years from the date of publication. Purchasers of American National Standards may receive current information on all standards by calling or writing the American National Standards Institute, 25 West 43rd Street, Fourth Floor, New York, NY 10036; 212.642.4900; or emailing info@ansi.org

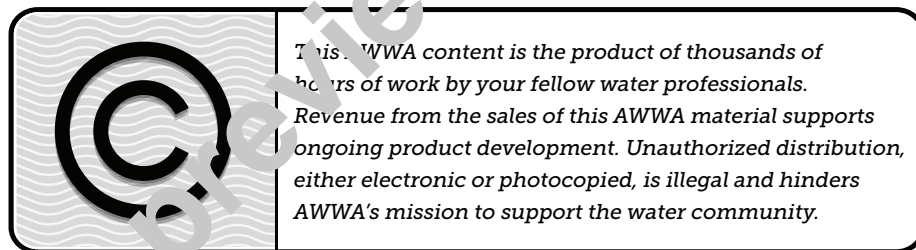

ISBN-13, print: 978-1-62576-199-6

eISBN-13, electronic: 978-1-61300-401-2

DOI: <http://dx.doi.org/10.12999/AWWA.C300.16>

All rights reserved. No part of this publication may be reproduced or transmitted in any form or by any means, electronic or mechanical, including photocopy, recording, or any information or retrieval system, except in the form of brief excerpts or quotations for review purposes, without the written permission of the publisher.

Copyright © 2017 by American Water Works Association
Printed in USA

Committee Personnel

The AWWA Standards Subcommittee on ANSI/AWWA C300, which reviewed and developed this standard, had the following personnel at the time:

Henry H. Bardakjian, *Chair*

S.A. Arnaout, Forterra Pressure Pipe Inc., Dallas, Texas	(AWWA)
H.H. Bardakjian, Consulting Engineer, Glendale, Calif.	(AWWA)
W.C. Duke, Bureau of Reclamation, Denver, Colo.	(USBR)
M. McReynolds, Metropolitan Water District of Southern California, Los Angeles, Calif.	(AWWA)
J. Olmos, Ameron Water Transmission Group, Rancho Cucamonga, Calif.	(AWWA)
A.E. Romer, AECOM, Orange, Calif.	(AWWA)
T.A. Tovey, CH2M, Bellevue, Wash.	(AWWA)

The AWWA Standards Committee on Concrete Pressure Pipe, which reviewed and approved this standard, had the following personnel at the time of approval:

Wayne R. Brunner, *Chair*

Richard J. Mueller, *Secretary*

Other Members

K.A. Danley, Des Moines Water Works, Des Moines, Iowa	(AWWA)
W.C. Duke, Bureau of Reclamation, Denver, Colo.	(USBR)
N.D. Faber, San Diego County Water Authority, Escondido, Calif.	(AWWA)
J.A. Fleming*, Standards Council Liaison, Greater Cincinnati Water Works, Cincinnati, Ohio	(AWWA)
J.C. Gehrig, Tarrant Regional Water District, Fort Worth, Texas	(AWWA)
J.G. Grunow, Louisville Water Company, Louisville, Ky.	(AWWA)
D.H. Marshall, Tarrant Regional Water District, Fort Worth, Texas	(AWWA)
N.A. Wagner, Los Angeles Department of Water and Power, Los Angeles, Calif.	(AWWA)

* Liaison, nonvoting

† Alternate

General Interest Members

H.H. Bardakjian, Consulting Engineer, Glendale, Calif.	(AWWA)
G.E.C. Bell, HDR Engineering Inc., Claremont, Calif.	(AWWA)
W.R. Brunzell, Brunzell Associates Ltd., Skokie, Ill.	(AWWA)
B.C. Coltharp, Freese and Nichols Inc., Fort Worth, Texas	(AWWA)
D. Dechant, Dechant Infrastructure Services, Aurora, Colo.	(AWWA)
F.S. Kurtz,* Standards Engineer Liaison, AWWA, Denver, Colo.	(AWWA)
S.A. McKelvie,† HDR Engineering Inc., Boston, Mass.	(AWWA)
J.J. Roller, CTL Group, Skokie, Ill.	(AWWA)
A.E. Romer, AECOM, Orange, Calif.	(AWWA)
T.A. Tovey, CH2M, Bellevue, Wash.	(AWWA)
A.W. Tremblay, Tipp City, Ohio	(AWWA)
M.S. Zarghamee, Simpson Gumpertz & Heger Inc., Waltham, Mass.	(AWWA)

Producer Members

S.A. Arnaout, Forterra Pressure Pipe Inc., Dallas, Texas	(AWWA)
G. Bizien,† Forterra Pressure Pipe Inc., St. Eustache, Quebec, Canada	(AWWA)
K.M. Brown, Vianini Pipe Inc., Somerville, N.J.	(AWWA)
G.A. Davidenko, Northwest Pipe Company, Saginaw, Texas	(AWWA)
M. DeFranco,† DECAST Ltd., Utopia, Ont., Canada	(AWWA)
V. DeGrande,† Ameron Water Transmission Group, Rancho Cucamonga, Calif.	(AWWA)
B.D. Keil,† Northwest Pipe Company, Helper, Utah	(AWWA)
R.I. Mueller, American Concrete Pressure Pipe Association, Orange, Calif.	(ACPPA)
J. Olmos, Ameron Water Transmission Group, Rancho Cucamonga, Calif.	(AWWA)
J.A. Tully, DECAST Ltd., Utopia, Ont., Canada	(AWWA)

* Liaison, nonvoting

† Alternate

Contents

All AWWA standards follow the general format indicated subsequently. Some variations from this format may be found in a particular standard.

SEC.	PAGE	SEC.	PAGE
Foreword		4.2	Drawings and Data to Be Provided by the Purchaser..... 6
I	Introduction..... vii	4.3	Data to Be Submitted by the Manufacturer 6
I.A	Background..... vii	4.4	Materials 7
I.B	History..... vii	4.5	Design..... 11
I.C	Acceptance..... viii	4.6	Fabrication 15
II	Special Issues..... ix	4.7	Fittings and Special Pipe 22
II.A	Chlorine and Chloramine Degradation of Elastomers ix	5	Verification
III	Use of This Standard..... ix	5.1	Inspection and Testing by the Purchaser 25
III.A	Purchaser Options and Alternatives ix	5.2	Tests..... 25
III.B	Modification to Standard..... x	5.3	Quality Assurance..... 26
IV	Major Revisions..... x	6	Delivery
V	Comments xi	6.1	Marking..... 26
Standard		6.2	Transportation 27
1	General	6.3	Affidavit of Compliance 27
1.1	Scope 1	Tables	
1.2	Purpose 1	1	Requirements for Pipe of Various Sizes 13
1.3	Application..... 2	2	Minimum Thickness of Steel for Fittings of Various Diameters..... 23
2	References 2		
3	Definitions 5		
4	Requirements		
4.1	Permeation 6		

This page intentionally blank.

Currently in preview, click buy full version

Foreword

This foreword is for information only and is not a part of ANSI/AWWA C300.

I. Introduction.

I.A. *Background.* Reinforced concrete pressure pipe of the cylinder type, first manufactured in 1919, consists of a welded steel cylinder with a steel joint ring welded at each end; a cage or cages of steel reinforcing bars or wire; an encasing wall of concrete; and a preformed gasket of rubber to provide the joint seal between adjacent pipes. The pipe is manufactured in sizes ranging from 30 in. (760 mm) to more than 144 in. (3,660 mm) in diameter and is generally made in 16-ft through 24-ft (4.8-m through 7.5-m) laying lengths.

Reinforced concrete pressure pipe, steel-cylinder type, is designed for the specific combination of internal pressure and external load required for the project in accordance with the procedures outlined in AWWA Manual M9, *Concrete Pressure Pipe*. This pipe is normally limited in working pressures to a maximum of 260 psi (1,790 kPa).

This type of pipe is used for transmission lines in irrigation, industrial, and domestic water supply systems, as well as for distribution, feeder mains and other uses (see Section III of the foreword).

I.B. *History.* In April 1943, the AWWA Board of Directors authorized the preparation of “Tentative Emergency Specifications for Concrete Pressure Pipe.” These tentative specifications, which described several types of pipe in a single document, served a useful purpose during World War II but became obsolete and were withdrawn.

The first standard prepared by AWWA Water Works Practice Committee 8320D—Reinforced Concrete Pipe, which was formed in 1946, described the manufacture of reinforced concrete pressure pipe, steel-cylinder type, not prestressed. The standard is now designated ANSI/AWWA C300. The first edition of this standard was approved as tentative on Dec. 11, 1947. It was revised and approved as a standard on Jan. 13, 1952. The second edition was approved as tentative on July 19, 1957, and made a standard on Jan. 27, 1964. Subsequent editions of ANSI/AWWA C300 were approved by the AWWA Board of Directors on Jan. 28, 1974; May 16, 1982; July 26, 1989; Feb. 2, 1997; June 13, 2004; and Jan. 23, 2011. This edition was approved on June 19, 2016.

Installation, design, and other data pertaining to this type of pipe are described by AWWA Manual M9, *Concrete Pressure Pipe*.

* American National Standards Institute, 25 West 43rd Street, Fourth Floor, New York, NY 10036.

I.C. *Acceptance.* In May 1985, the US Environmental Protection Agency (USEPA) entered into a cooperative agreement with a consortium led by NSF International (NSF) to develop voluntary third-party consensus standards and a certification program for direct and indirect drinking water additives. Other members of the original consortium included the Water Research Foundation (formerly AwwaRF) and the Conference of State Health and Environmental Managers (COSHEM). The American Water Works Association (AWWA) and the Association of State Drinking Water Administrators (ASDWA) joined later.

In the United States, authority to regulate products for use in, or in contact with, drinking water rests with individual states.* Local agencies may choose to impose requirements more stringent than those required by the state. To evaluate the health effects of products and drinking water additives from such products, state and local agencies may use various references, including

1. Specific policies of the state or local agency.
2. Two standards developed under the direction of NSF: NSF/ANSI 60, Drinking Water Treatment Chemicals—Health Effects, and NSF/ANSI 61, Drinking Water System Components—Health Effects.
3. Other references, including AWWA standards, *Food Chemicals Codex*, *Water Chemicals Codex*,[‡] and other standards considered appropriate by the state or local agency.

Various certification organizations may be involved in certifying products in accordance with NSF/ANSI 61. Individual states or local agencies have authority to accept or accredit certification organizations within their jurisdictions. Accreditation of certification organizations may vary from jurisdiction to jurisdiction.

Annex A, “Toxicology Review and Evaluation Procedures,” to NSF/ANSI 61 does not stipulate a maximum allowable level (MAL) of a contaminant for substances not regulated by a USEPA final maximum contaminant level (MCL). The MALs of an unspecified list of “unregulated contaminants” are based on toxicity testing guidelines (noncarcinogens) and risk characterization methodology (carcinogens). Use of Annex A procedures may not always be identical, depending on the certifier.

ANSI/AWWA C300 does not address additives requirements. Users of this standard should consult the appropriate state or local agency having jurisdiction in order to

* Persons outside the United States should contact the appropriate authority having jurisdiction.

† NSF International, 789 North Dixboro Road, Ann Arbor, MI 48105.

‡ Both publications available from National Academy of Sciences, 500 Fifth Street, NW, Washington, DC 20001.

1. Determine additives requirements, including applicable standards.
2. Determine the status of certifications by parties offering to certify products for contact with, or treatment of, drinking water.
3. Determine current information on product certification.

II. Special Issues. Special issues are addressed in AWWA Manual M9, *Concrete Pressure Pipe*, and in Sec. II.A.

II.A. *Chlorine and Chloramine Degradation of Elastomers.* The selection of materials is critical for water service and distribution piping in locations where there is a possibility that elastomers will be in contact with chlorine or chloramines. Documented research has shown that elastomers such as gaskets, seals, valve seats, and encapsulations may be degraded when exposed to chlorine or chloramines. The impact of degradation is a function of the type of elastomeric material, chemical concentration, contact surface area, elastomer cross section, and environmental conditions as well as temperature. Careful selection of, and specifications for, elastomeric materials and the specifics of their application for each water system component should be considered to provide long-term usefulness and minimum degradation (swelling, loss of elasticity, or softening) of the elastomer specified.

III. Use of This Standard. It is the responsibility of the user of an AWWA standard to determine that the products described in that standard are suitable for use in the particular application being considered.

III.A. *Purchaser Options and Alternatives.* Purchasers are advised that, while this standard presents information on materials and procedures of manufacture of the pipe, it does not contain all of the engineering information needed to prepare a complete specification for a particular pipeline installation. A specific installation may require more restrictive provisions than those in the standard and most certainly will require additional design and installation features.

Reference to AWWA Manual M9, *Concrete Pressure Pipe*, should be considered a supplement to the use of this standard, and information in the manual should not be regarded as superseding any portion of this standard. The purpose of AWWA Manual M9 is to provide information concerning some of the various subjects to be considered in, and the minimum standard of practice for, the design and installation of concrete pressure pipelines.

The following information should be provided by the purchaser:

1. Standard used—that is, ANSI/AWWA C300, Reinforced Concrete Pressure Pipe, Steel-Cylinder Type, of latest revision.

2. Whether compliance with NSF/ANSI 61, Drinking Water System Components—Health Effects, is required.
3. Manner of storage and delivery, if required of the manufacturer.
4. Working pressure, surge pressure, field-test pressure, external loading conditions, and method of bedding and backfilling (Sec. 4.2.2).
5. If detailed drawings and schedules are to be submitted for review (Sec. 4.3.1).
6. If the manufacturer is not permitted to supply pipe from inventory (Sec. 4.3.1).
7. If a tabulated layout schedule will be required (Sec. 4.3.2).
8. Details of other federal, state or provincial, and local requirements (Sec. 4.4).
9. Type of cement required, if there is a preference (Sec. 4.4.1.1).
10. If the manufacturer is not permitted to use pozzolanic materials as a cement replacement (Sec. 4.4.1.1).
11. If aggregate samples will be required (Sec. 4.4.4).
12. If submission of the type and amount of admixture will be required (Sec. 4.4.6).
13. If submission of manufacturer's design calculations will be required (Sec. 4.5.2).
14. If elliptical reinforcement is acceptable (Sec. 4.6.2 and AWWA Manual M9).
15. If submission of welding procedure specifications will be required (Sec. 4.6.3).
16. Variance in curing, if permitted (Sec. 4.6.7.1).
17. If details of specials and fittings are to be provided by the manufacturer (Sec. 4.7.1).
18. If the purchaser desires to inspect the material, pipe, and fittings at the manufacturer's plant (Sec. 5.1.1).
19. If any material or manufacturing test reports will be required (Sec. 5.1.2).
20. If steel test specimens will be required (Sec. 5.2.5).
21. If testing of welds in reinforcing bars is required (Sec. 5.2.7).
22. If identification marks referenced to layout drawings and schedules are required (Sec. 6.1).
23. If an affidavit of compliance will be required (Sec. 6.3).

11.B. *Modification to Standard.* Any modification to the provisions, definitions, or terminology in this standard must be provided by the purchaser.

IV. Major Revisions. Major changes made to the standard in this edition include the following:

1. New language on chlorine and chloramine degradation of elastomers has been added to the Special Issues section (Sec. II.A) of the foreword.

V. Comments. If you have any comments or questions about this standard, please call AWWA Engineering and Technical Services at 303.794.7711, FAX at 303.795.7603; write to the department at 6666 West Quincy Avenue, Denver, CO 80235-3098; or email at standards@awwa.org.

This page intentionally blank.



**American Water Works
Association**

Dedicated to the World's Most Important Resource®

ANSI/AWWA C300-16
(Revision of ANSI/AWWA C300-11)

AWWA Standard

Reinforced Concrete Pressure Pipe, Steel-Cylinder Type

SECTION 1: GENERAL

Sec. 1.1 Scope

This standard describes the manufacture of reinforced concrete cylinder pipe in sizes 30 in. to 144 in. (760 mm to 3,660 mm), inclusive. Larger sizes have been manufactured based on the concepts of this standard. This type of pipe is designed for the internal pressure, external loads, and bedding conditions designated by the purchaser. This standard does not include requirements for design, handling, delivery, laying, field testing, or disinfection of pipe. Refer to AWWA Manual M9, *Concrete Pressure Pipe*, for information on these topics.

1.1.1 *Essential requirements.* The pipe shall have the following principal features: a welded steel cylinder with steel joint rings welded to its ends; a reinforcing cage or cages of steel bars, wire, or welded wire reinforcement; a wall of concrete encasing the steel cylinder and reinforcing cage or cages inside and outside of the steel cylinder; and a joint with a preformed gasket of rubber, designed so that the joint will be watertight under all conditions of service.

Sec. 1.2 Purpose

The purpose of this standard is to provide the minimum requirements for reinforced concrete pressure pipe, steel-cylinder type, including fabrication and testing requirements.